

MODIFIED HALLOYSITE NANOTUBES AS CARRIER
FOR ANTIMICROBIALS AGENT IN WOUND HEALING
MATERIALS

BY

NADER M.I ABUHAMED

A dissertation submitted in fulfilment of the requirement for
the degree of Master of Science (Materials Engineering)

Kulliyyah of Engineering
International Islamic University Malaysia

May 2021

ABSTRACT

Plastic waste has become a significant issue globally, especially in the medical field, where most of the products are petroleum-based plastics. In this research, polysaccharide base films were utilized to overcome this issue. Polysaccharide materials such as thermoplastic sago starch (TPSS) promote wound healing; however, an infection is more likely to occur. Halloysite nanotubes (HNTs) are a biocompatible material that is used in medical applications. In this research, halloysite was modified by dispersing it with chloramphenicol solution. Chloramphenicol was loaded into halloysites using a magnetic stirrer. Thermoplastic sago starch (TPSS)/modified halloysite (MHNTs) biocomposite films were developed using the solution casting method. In addition, starch/ halloysite biocomposites films also were produced for comparison. Surface morphology characterization was done for the halloysite nanotubes, where it showed agglomerations of the modified halloysite. The scanning electron microscopy (SEM) images showed a good dispersion of the natural halloysite in the polymer matrix compared to the modified halloysite. Besides, modified halloysite shows higher agglomeration with further addition. X-ray diffraction spectra of the starch films showed an alteration with the addition of halloysite nanotubes, indicating intercalation of halloysites in the TPSS matrix. FTIR peaks of TPSS also showed changes with the addition of halloysite. The tensile properties demonstrated the mechanical properties of the halloysite/ thermoplastic sago starch. HNT and MHNT at 0.25 wt.% had slightly improved the tensile strength of the TPSS from 3.69 MPa to 4.11 and 3.76 MPa, respectively. However, the tensile strain was reduced when halloysite was introduced to the polymer matrix. The water absorption was decreased from 72.96% to 58.62% at 0.25 and 1 wt.% of HNT. Meanwhile, MHNT reduced the water absorption rate from 72.96% and 53.13% at 0.25 and 1 wt.% of MHNT, respectively. This reduction is attributed to its encapsulation of the chloramphenicol antibiotics which is a highly hydrophobic substance. Halloysite in nature is not an antimicrobial agent, and this was observed from the disc diffusion method. However, when HNT was modified using an antimicrobial substance, it successfully showed good susceptibility to bacterial culture. This indicates the ability of MHNTs to be used as an antibacterial carrier for wound dressing materials. The soil burial method was used to evaluate the biodegradability of TPSS biocomposites. MHNT has significantly reduced the biodegradability of TPSS compared to pure HNT. This leads to the fact that MHNT had good antimicrobial properties, which lead to the MHNT/TPSS to withstand the degradation from microbes in the soil. Results showed that halloysite could be a potential carrier for antibacterial agents. The thermoplastic sago starch can be an effective composite when incorporating with modified halloysite to withstand bacterial attacks. This research opens new doors for halloysite nanotubes to be further studied for carrying antibacterial substances or other drugs.

خلاصة البحث

أصبحت النفايات البلاستيكية مشكلة رئيسية في العالم، خاصة في المجال الطبي حيث معظم المنتجات عبارة عن مواد بلاستيكية قائمة على البترول. في هذا البحث تم استخدام مواد عديد السكريد للتغلب على هذه المشكلة. تعمل مواد السكريات المتعددة مثل نشا الساجو البلاستيكي الحراري (TPSS) على تعزيز التئام الجروح ولكن من المرجح أن تحدث العدوى. تعد أنابيب هالوسايت النانوية (HNTs) متوافقة حيويًا بحيث تُستخدم في التطبيقات الطبية. في هذا البحث تم تعديل هالوسايت عن طريق اذابته بمحلول الكلورامفينيكول. تم مزج وادخال الكلورامفينيكول في داخل انابيب الهالوسايت (HNTs) وعلى اسطحها باستخدام التحريك المغناطيسي. تم تطوير أفلام نشا الساجو البلاستيكي الحراري (TPSS) / والهالوسايت المعدل (MHNTs) باستخدام طريقة صب المحلول. بالإضافة إلى ذلك، تم إنتاج نشا الساجو البلاستيكي الحراري (TPSS) / والهالوسايت غير المعدل (HNTs) من أجل المقارنة. تم فحص سطح أنابيب الهالوسايت النانوية بالميكروسكوب، حيث تُظهر تكتلات وتجمعات من هالوسايت المعدل. بالإضافة إلى ذلك، أظهرت صور الفحص المجهر الإلكتروني (SEM) توزيعًا جيدًا للهالوسايت في سطح البوليمر مقارنةً بالهالوسايت المعدل حيث يُظهر تكتلاً أعلى عند زيادته. أظهرت أطياف الأشعة السينية لأغشية النشا تغييراً مع إضافة أنابيب الهالوسايت النانوية وهذا يشير وجود الهالوسايت في سطح مركب البوليمر TPSS. كما أظهرت قمم FTIR لـ TPSS تغييرات مع إضافة الهالوسايت (HNT). أظهرت خصائص الشد الخواص الميكانيكية لنشا الساجو / اللدائن الحرارية. حسنت HNT و MHNT عند 0.25% بشكل طفيف قوة الشد لـ TPSS من 3.69 ميغا باسكال إلى 4.11 و 3.76 ميغا باسكال على التوالي. ومع ذلك، قل إجهاد الشد عندما تم إدخال هالوسايت إلى مصفوفة البوليمر. تم تقليل امتصاص الماء من 72.96% إلى 58.62% عند 0.25 و 1% من HNT. وفي الوقت نفسه، خفضت MHNT معدل امتصاص الماء من 72.96% و 53.13% عند 0.25 و 1% من MHNT على التوالي. عندما يتم مزج HNTs في مصفوفة TPSS فإنها تقلل من امتصاص الماء. ومع ذلك، فإن إضافة MHNT قد قللت أيضًا من امتصاص الماء أكثر من HNT. وهذا يُعزى إلى تغليفه بمضادات الكلورامفينيكول الحيوية وهي مادة شديدة الكراهية للماء. هالوسايت في الطبيعة ليس عاملاً مضاداً للميكروبات وقد لوحظ هذا من فحص البكتيريا الذي تم إجراؤه. ومع ذلك، عندما تم تعديل الهالوسايت باستخدام مادة مضادة للميكروبات، فقد أظهر بنجاح قابلية جيدة للبيئة البكتيرية. هذا يشير إلى قدرة MHNTs على استخدامها كناقل مضاد للجراثيم لمواد تضميد الجروح. تم استخدام طريقة الدفن في التربة لتقييم قابلية التحلل البيولوجي للمركبات الحيوية TPSS وقد قلل MHNT بشكل كبير من قابلية التحلل البيولوجي لـ TPSS مقارنة بـ HNT النقي. هذا يؤدي إلى حقيقة أن MHNT له خصائص جيدة مضادة للميكروبات والتي تؤدي إلى MHNT / TPSS لتحمل التحلل من الميكروبات في التربة. أظهرت النتائج أن الهالويسيت يمكن أن يكون ناقلاً محتملاً للعوامل المضادة للبكتيريا ويمكن أن تكون لدائن نشا الساجو الحرارية مركبًا فعالاً عند دمجها مع هالوسايت المعدل لمقاومة الهجمات البكتيرية. يفتح هذا البحث أبوابًا جديدة لأنابيب هالوسايت النانوية لمزيد من الدراسة لحمل مادة مضادة للبكتيريا أو أدوية أخرى.

APPROVAL PAGE

I certify that I have supervised and read this study and that in my opinion, it conforms to acceptable standards of scholarly presentation and is fully adequate, in scope and quality, as a dissertation for the degree of Master of Science (Materials Engineering)



.....
Zuraida Ahmad
Supervisor

.....
Norshahida Sarifuddin
Co-Supervisor

I certify that I have read this study and that in my opinion it conforms to acceptable standards of scholarly presentation and is fully adequate, in scope and quality, as a dissertation for the degree of Master of Science (Materials Engineering)

.....
Nur Ayuni binti Jamal
Internal Examiner

.....
Zahurin Binti Halim
Internal Examiner

This dissertation was submitted to the Department of Manufacturing and Materials Engineering and is accepted as a fulfilment of the requirement for the degree of Master of Science (Materials Engineering)

.....
Erry Yulian Triblas Adesta
Head, Department of
Manufacturing and Materials
engineering

This dissertation was submitted to the Kulliyah of Engineering and is accepted as a fulfilment of the requirement for the degree of Master of Science (Materials Engineering)

.....
Sany Izan Ihsan
Dean, Kulliyah of Engineering

DECLARATION

I hereby declare that this dissertation is the result of my own investigations, except where otherwise stated. I also declare that it has not been previously or concurrently submitted as a whole for any other degrees at IIUM or other institutions.

Nader M.I Abuhamed

Signature

Date

INTERNATIONAL ISLAMIC UNIVERSITY MALAYSIA

**DECLARATION OF COPYRIGHT AND AFFIRMATION OF
FAIR USE OF UNPUBLISHED RESEARCH**

**MODIFIED HALLOYSITE NANOTUBES AS CARRIER FOR
ANTIMICROBIALS AGENT IN WOUND HEALING
MATERIALS**

I declare that the copyright holders of this dissertation are jointly owned by the student and IIUM.

Copyright © 2021 Nader M.I Abuhamed and International Islamic University Malaysia. All rights reserved.

No part of this unpublished research may be reproduced, stored in a retrieval system, or transmitted, in any form or by any means, electronic, mechanical, photocopying, recording, or otherwise without prior written permission of the copyright holder except as provided below

1. Any material contained in or derived from this unpublished research may be used by others in their writing with due acknowledgement.
2. IIUM or its library will have the right to make and transmit copies (print or electronic) for institutional and academic purposes.
3. The IIUM library will have the right to make, store in a retrieved system and supply copies of this unpublished research if requested by other universities and research libraries.

By signing this form, I acknowledged that I have read and understand the IIUM Intellectual Property Right and Commercialization policy.

Affirmed by NADER M.I ABUHAMED

.....
Signature

.....
Date

ACKNOWLEDGEMENTS

Praise be to Allah, the most merciful and most compassionate, for his blessing and for giving me the opportunity, strength, and time to complete my dissertation.

My utmost pleasure to dedicate this work to my dear parents and my family, who granted me the gift of their unwavering belief in my ability to accomplish this goal: thank you for your support and patience.

A special thanks to my supervisor, Assoc. Prof. Dr. Ir. Zuraida Ahmad for her continuous support, encouragement, guidance, and leadership, and for that, I will be forever grateful. I would also like to thank my co-supervisor, Dr. Norshahida Binti Sarifuddin, for her support, guidance, and confidence in me, which inspired me to finish my master's degree.

I want to express my deep appreciation to all the technical staff in laboratories and the Department of Manufacturing and Materials Engineering staff for their assistance and cooperation throughout my research period. And I would also like to thank the staff in the postgraduate office and the department coordinator Assoc. Prof. Mohd. Hanafi bin Ani and all the administrative officers for their assistance and guidance throughout my studies.

I wish to express my appreciation and thanks to those who provided their time, effort, and support for this project. To the members of my dissertation committee, thank you for sticking with me.

TABLE OF CONTENTS

Abstract	ii
Abstract in Arabic	ii
Approval Page.....	iv
Declaration.....	v
Copyright Page.....	vi
Acknowledgements.....	vii
Table of Contents	viii
List of Tables	x
List of Figures	xi
List of Abbreviations	xv
List of Symbols	xvi
CHAPTER ONE: INTRODUCTION	1
1.1 Background.....	1
1.2 Statement of The Problem	3
1.3 Research Objectives.....	4
1.4 Significance of Research	5
1.5 Scope of The Study.....	5
1.6 Dissertation Organization	6
CHAPTER TWO: LITERATURE REVIEW.....	7
2.1 Introduction.....	7
2.2 Type Of Wounds.....	7
2.2.1 Chronic Wounds	8
2.2.2 Acute Wounds.....	8
2.3 Wound Healing Process.....	10
2.4 Polysaccharide In Wound Healing Applications	14
2.5 Starch	19
2.6 Halloysite Nanotubes.....	28
2.7 Polysaccharide-Halloysite Nanotube Composites.....	36
2.8 Fabrication And Performance Of Starch -Halloysite Nanotubes Composites	38
2.8.1 Purification of HNTs.....	38
2.8.2 Polysaccharide- HNTs Composites Films	39
2.9 Antimicrobial Activities of Halloysite Nanocomposites.....	52
2.10 Challenges and Opportunities.....	55
2.11 Summary.....	57
CHAPTER THREE: METHODOLOGY	59
3.1 Introduction.....	59
3.2 Materials Preparation.....	61
3.3 Fabrication of Wound Dressing Thin Films	63
3.3.1 Formulating of Thin Films	63
3.3.2 Mixing and Casting Process TPSS/HNT and TPSS/MHNT	64
3.4 Test Methods	64

3.4.1 Water Absorption	64
3.4.2 Surface Morphology	66
3.4.3 Phase Changes by XRD Analysis	66
3.4.4 Chemical Characterization	66
3.4.5 Tensile Test	67
3.4.6 Biodegradability	68
3.4.7 Antimicrobial Inhibition Test.....	69
3.5 SUMMARY	71
CHAPTER FOUR: RESULTS AND DISCUSSION	72
4.1 Introduction.....	72
4.2 Water Absorption.....	73
4.3 Surface Morphology	75
4.3.1 Halloysite Nanotubes	75
4.3.2 Thermoplastic Sago Starch	77
4.4 XRD	81
4.5 FTIR.....	87
4.6 Tensile Strength	91
4.7 Biodegradability	95
4.8 Antimicrobial Inhibition Test	102
CHAPTER FIVE: CONCLUSION AND RECOMMENDATION.....	105
5.1 CONCLUSION	105
5.2 RECOMMENDATION	108
REFERENCES.....	110

LIST OF TABLES

Table 3.1	Formulation of the thin film with unmodified halloysite nanotubes	63
Table 3.2	Formulation of the Thin film with modified halloysite nanotubes (MHNT)	63
Table 4.1	d-spacing values of HNTs and HNTs embedded in TPSS composites	85
Table 4.2	d-spacing values of HNTs and HNTs embedded in TPSS composites	87

LIST OF FIGURES

Figure 2.1	Wound classification	8
Figure 2.2	Types of Acute Wound	9
Figure 2.3	Cross-section of skin and Panniculus	12
Figure 2.4	Wound healing phases	13
Figure 2.5	Polysaccharide's structure	15
Figure 2.6	Structures of starch components (a) amylose and (b) amylopectin	19
Figure 2.7	SEM images of sago 1, sago 2, corn, and potato starch at 1500 × magnification	21
Figure 2.8	Induction of excision wound and observation of wound healing. A (Wound only, without membrane), B (wound + CCSM), and C (wound+ CCSM loaded with <i>P. granatum</i> extract). CCSM Chitosan-collagen-starch membrane	25
Figure 2.9	Antibacterial activity of <i>P. granatum</i> pericarp aqueous extract loaded CCSM on <i>Pseudomonas aeruginosa</i> . 1 CCSM only, 2 CCSM with de-ionized water, 3 CCSM with gentamycin sulfate (Positive control), and 4 CCSM with <i>P. granatum</i> extract. CCSM Chitosan-collagen-starch membrane	26
Figure 2.10	Photographic evaluation of wound healing. A faster rate of wound healing was observed in the SG–SY–G–C treated wounds on the 16th day (f) and 18th day (d)	28
Figure 2.11	Halloysite nanotube minerals	30
Figure 2.12	Halloysite layer structure	31
Figure 2.13	SEM and TEM image of HNTs	34
Figure 2.14	Structure of halloysite nanotube	35
Figure 2.15	FE-SEM image of HNTs on Si-Wafer (a) and Schematic Illustration of Crystalline Structure of HNTs (b)	39
Figure 2.16	FESEM micrographs of the HNT/TPSS nanocomposite films at (a) 0, (b) 0.25, (c) 0.5, (d) 1.0, (e) 3.0 and (f) 5.0 wt.% of HNT contents	40

Figure 2.17	Tensile fracture Morphology of HNT/TPSS nanocomposite films for (a) 0, (b) 0.25, (c) 0.5, (d) 1.0, (e) 3.0 and (f) 5.0 wt.% of HNT	41
Figure 2.18	SEM of treated halloysite (a, b) and halloysite/starch films with 3 wt.% (C, d) and 7 wt. % halloysite (e, f)	43
Figure 2.19	FTIR spectra (a, b) and (c) XRD pattern of polysaccharides /HNTs composites	46
Figure 2.20	illustration of bio-nano composite hydrogel formation	48
Figure 2.21	TGA curves of HNT/TPSS nanocomposites	50
Figure 2.22	The degradation condition of the nanocomposites after 60 days	51
Figure 2.23	The weight loss of nanocomposite due to degradation after certain burial days	52
Figure 2.24	Antimicrobial study of HNT/ chitosan loaded with various HNT content	53
Figure 2.25	(a–c) images of disk diffusion test for the PLLA-HNTs@Ag scaffolds after for 3, 7, and 14 days; (d) the diameter of the inhibition zones; (e–i) the adhesion morphology of E. coil on the scaffolds after culture for one day	54
Figure 2.26	Antimicrobial activities of the biocomposite at different HNTs (H) and Nisin (N)	55
Figure 3.1	Flowchart of the research process	60
Figure 3.2	Modified HNT solution	62
Figure 3.3	Modified HNT particles: (a) HNT after drying solution, (b) HNT after ball milling, and (c) HNT after sieving and drying in the oven.	62
Figure 3.4	Water absorption test setup	65
Figure 3.5	The standard size of samples for tensile test	67
Figure 3.6	Mixed LB broth ready to autoclave, (b): autoclave machine set the temperature to 120 for 15 min to sterilize the solution, (c) Erlenmeyer flask that contains the bacteria and broth was rotated for 24 hours at a speed of 60 rpm and the temperature was set to 37 °C	69

Figure 3.7	Swap pattern on the agar plates will ensure an even distribution of the bacteria on top of the agar surface	70
Figure 4.1	Water absorption for TPSS/HNT & TPSS/MHNT composites	74
Figure 4.2	HNT structure under TEM	75
Figure 4.3	SEM micrograph HNT & MHNT – (a) HNT at 3.000 X, (b) MHNT at 3.000 X, (c) MHNT at 10.000 X and (d) HNT at 10.000X	77
Figure 4.4	SEM micrograph of thermoplastic sago starch	78
Figure 4.5	SEM micrograph of TPSS/HNT & TPSS/MHNT at 3.000 X – (a) 0.25 wt.% HNT, (b) 0.5 wt.% HNT, (c) 0.75 wt.% HNT, (d) 1.0 wt.% HNT, (e) 0.25 wt.% MHNT, (f) 0.5 wt.% MHNT, (g) 0.75 wt.% MHNT and (h) 1.0 wt.% HNT	80
Figure 4.6	X-ray Diffractograms (XRD) of HNT and MHNT	81
Figure 4.7	X-ray Diffractograms (XRD) of HNT	83
Figure 4.8	X-ray Diffractograms (XRD) of HNT/TPSS nanocomposite films	84
Figure 4.9	X-ray Diffractograms (XRD) of MHNT/TPSS nanocomposite films	86
Figure 4.10	FTIR spectra of plasticized starch matrix (TPSS) containing 0, 0.25, 0.5, 0.75 and 1 wt.% of HNT for wavenumber between 750 cm ⁻¹ to 4000cm ⁻¹	89
Figure 4.11	FTIR spectra of plasticized starch matrix (TPSS) containing 0, 0.25, 0.5, 0.75 and 1 wt.% of MHNT for wavenumber between 750 cm ⁻¹ to 4000cm ⁻¹	91
Figure 4.12	Tensile strength of HNT/TPSS and MHNT/TPSS nanocomposite films	93
Figure 4.13	Tensile strain of HNT/TPSS and MHNT/TPSS Nanocomposite films	95
Figure 4.14	The weight loss of nanocomposites due to degradation after certain burial days in wet soil	96
Figure 4.15	The degradation condition of the nanocomposites after certain burial days in wet soil	98

Figure 4.16	The weight loss of nanocomposite due to degradation after certain burial days in dry soil	100
Figure 4.17	The degradation condition of the nanocomposites after certain burial days in dry soil	101
Figure 4.18	Anti-microbial disk diffusion test for TPSS/HNT & TPSS/HNT composites	103
Figure 4.19	Area of inhibition zone for TPSS/HNT & TPSS/HNT composites	104

LIST OF ABBREVIATIONS

C	Collagen
CCSM	Chitosan-Collagen-Starch Membrane
cm	Centimeter
Cm ³	Centimeter cubic
e.g.	exempli gratia
ECM	Extracellular Matrix
Et al.	Et Alia
etc.	Et cetera
FE-SEM	Field Emission Scanning Electron Microscopy
FTIR	Fourier-Transform Infrared Spectroscopy
G	Glutaraldehyde
g	Gram
GAGs	Glycosaminoglycan
GPa	Giga pascal
HA	Hyaluronic Acid
HNT	Halloysite Nanotubes
ml	Millimeter
MHNT	Modified Halloysite Nanotubes
MIC	Minimum Inhibitory Concentrations
Min	Minute
µm	micrometer
MPa	Mega pascal
N	Newton
NaCl	Sodium chloride
Nm	Nanometer
PLLA	poly-L-lactic acid
PVA	Polyvinyl Alcohol
rpm	Revelation per minute
SEM	Scanning Electron Microscope
SG	Sago Starch
SY	soya protein
TEM	Transmission Electron Microscopy
TPSS	Thermo Plastic Sago Starch
WHO	World Health Organization
Wt.%	Weight percent
XRD	X-Ray Diffraction

LIST OF SYMBOLS

%	Percentage
W	Weight
W_a	Water absorption
ρ	Density
m_a	Mass after
m_b	Mass before
L	Length
W_m	Moisture content
b	Width
A	Area
d	Depth
ε	Strain
σ	Stress
t	Thickness

CHAPTER ONE

INTRODUCTION

1.1 BACKGROUND

Wound and injuries had always been one of the significant problems for public health. The world health organization (WHO) has announced in 2000 that around 5 million people died from injuries. Moreover, in the same year, Malaysia had 13,401 injury cases, and it was estimated that 440 cases were deadly (Hasni, Junainah, & Jamaliah, 2003). In addition to mortality, the formation and healing process of wounds is a minor problem. However still, it is considered a big issue because it might lead to other major health problems. The number of injuries that occur every year worldwide are countless due to surgical procedures, ulcers, and burns that do not heal. A wound is a physical injury that usually damages the underlying tissues, and it is considered one of the most extensive clinical challenges in the world (Merriam & Webster. 2015). Some wounds like foot and pressure ulcers occur because of complications of some diseases such as diabetes, and these wounds are called chronic wounds. There is another type of wound called acute wounds, which are caused by skin injuries. These wounds are less harmful than chronic wounds because they can be healed more easily (Hasni, Junainah, & Jamaliah, 2003). Throughout history, several wound healing methods have been used to improve the healing process of wounds. Although wounds can heal naturally on their own, some factors delay wound healing, such as bacterial infections or exudate production at the wound surface. Therefore, the treatment and management of wounds are essential aspects to avoid the mentioned problems. Moreover, the market value for

care products used to treat wounds was estimated at 62.6 billion MYR in 2010, reflecting an increase in global clinical demand for those products (Sen et al., 2009).

The dressing provides wounds with the right environment under certain pathological conditions that make them heal at a maximum rate while giving a cosmetically acceptable appearance; they protect the wound from external influences and keep them moist to ensure proper healing. Modern dressings absorb wound exudate to control the healing process. Interestingly, to improve the absorption of wound exudates, dressings should be incorporated with a bioactive material such as polysaccharides (Sweeney, Mirafteb & Collyer, 2012). It is important to note that wound treatment interventions like dressings could support and accelerate the healing process. Hence, selecting the right wound healing materials by considering the healing ability and antimicrobial activity are essential aspects of dressing innovation. Polysaccharides are biologically derived polymers that had been extensively used as wound healing dressing material. And this is because of their availability, versatility, biocompatibility, and antimicrobial properties (Chen & Chang, 2008). Chitin, cellulose, starch, and glycogen are types of polysaccharide which have been extensively reported to be a suitable material in the medical industry, thus in this project, the sago starch (SG) polysaccharide is proposed as a potential candidate for fabricating of the films.

On the other hand, halloysite nanotubes (HNT) would help increase the mechanical properties and be an effective candidate as antimicrobial agents in wound healing application. HNT has a hollow structure, which has a tunable surface property and capable of encasing antiseptics. One of the most practical features of HNT is that they do not require expensive and high energy-consuming processes of exfoliation. Several reports were devoted to producing polymeric films and membranes containing antibacterial compounds incorporated with HNT (Morrison, Misra & Williams. 2016).

Therefore, the preparation and characterization of thermoplastic sago starch- halloysite nanotube composites, as wound healing application, will be presented in the later section.

1.2 STATEMENT OF THE PROBLEM

Polymers are materials that are suitable for all medical applications due to their vast and varied properties. In the past decade, plastic waste has become a significant issue globally, especially in the medical field, where most of the products are petroleum-based plastics. These plastics are harmful to people and the environment because petroleum plastics are non-biodegradable and very damaging. An appropriate wound dressing material should extract exudates and toxic substances from the surfaces of the wound, facilitate gaseous exchange, protect the wound from bacterial infection, retain high moisture at the wound/dressing site, and it should be removed safely without damaging the wound (Dhivya, Padma & Santhini, 2015). Many researchers have adopted the use of biopolymers since there are more environmentally friendly, and most importantly, biocompatible many in the medical application (Waghmare et al., 2018; Adeli, Khorasani & Parvazinia, 2018; Hassan et al., 2017; Baghaie et al., 2017; Amal et al., 2015). Films are the most ideal for wound dressing, and biopolymers-based material would be used as a based material because of its non-toxicity and biocompatibility compare to synthetic polymers. Polysaccharide polymers such as thermoplastic sago starch (TPSS) films have been successfully developed at IIUM (Ahmad, Hermain & Abdul Razak, 2015; Ahmad, Hermain & Abdul Razak, 2018). Besides, researchers have proven polysaccharides starches to be valid materials for wound dressing applications (Mandal et al., 2014; Amal et al., 2015). Polysaccharides

wound dressing materials such as starch promote and speed up the healing process during the wound healing process. However, starch hydrophilicity absorbs the exudates from the wounds during the healing process, which causes most likely promotes a bacterial infection that slows the healing process. Therefore, an antimicrobial agent needs to be used to overcome this issue (Mandal et al., 2014; Ramnath et al., 2012).

Halloysite nanotubes (HNT) have been used widely in drug delivery and tissue engineering scaffolds in the medical field. Halloysite does not have any antibacterial effect, and many studies reported that HNT needs to be modified to have the antibacterial impact (Kurczewska et al., 2017; Makaremi et al., 2017; Biddeci et al., 2016). In this research, modified HNT is proposed as the antibacterial filler for the wound dressing film. The advantage of the halloysite as the antibacterial carrier or filler is due to its hollow structure. Therefore, besides the HNT is reported to have a good impact on polymer composites' mechanical and thermal properties with a little bit of modification, it is expected to give suitable antimicrobial activities.

1.3 RESEARCH OBJECTIVES

The study aims to develop sago starch (SG) wound dressing incorporated with Halloysite nanotubes (HNT) as a carrier for antimicrobial agents for wound healing.

And to obtain this aim, several objectives need to be achieved:

- 1- To characterize the microstructure of halloysite nanotubes and TPSS / HNT nanocomposites. In addition to identifying the functional groups and crystallinity of the nanocomposites.

- 2- To evaluate the effect of unmodified halloysite nanotube and modified halloysite content on the physical (water absorption), mechanical (tensile), and degradability properties of the TPSS/HNT nanocomposite films.
- 3- To investigate the antimicrobial properties of TPSS/HNT nanocomposite using Kirby-Bauer disk diffusion method.

1.4 SIGNIFICANCE OF RESEARCH

This research introduced a wound dressing developed from biocompatible, nontoxic, inexpensive, widely available, and biodegradable resources. The produced biocomposite was made from sago starch, halloysite nanotubes, distilled water, and plasticizer glycerol in casted films. This developed biocomposite reduced the dependency on synthetic polymer materials used in the wound dressing industry since that waste is harmful to the environment and costly to dump it. Sago starch is widely available in Malaysia. With this new era of advanced biomaterial to replace synthetic polymers, it opened many doors in the research industry to utilize such materials for medical application. Halloysite is a well-known material used in drug delivery and many medical applications. In this research, tuned and modified halloysite opened new doors for wound dressing applications, especially with biocompatible sago starch.

1.5 SCOPE OF THE STUDY

This scope of the research focuses on the development and preparation of biocompatible wound dressing films of sago starch filled with halloysite nanotubes (HNT). This research evaluated the effect of modified halloysite nanotubes content on the sago starch at different loadings. HNT was modified by mixing it with antibiotics in

a magnetic stirrer until completely dissolved. A comparative study compared the addition of unmodified HNT & modified HNT to thermoplastic sago starch and their effects on antimicrobial activities, chemical bonding, crystallinity, biodegradability, microstructure, physical and mechanical properties of the wound dressing films.

1.6 DISSERTATION ORGANIZATION

Five chapters organize this research work. Chapter one introduces the wound dressings and the environmental and health issues that could result from it and ways to overcome these problems; it also shows the objectives of this research and the significance and scope of this study. Chapter two is a theoretical description of the sago starch, halloysite nanotubes, and reviews of the recent literature of their uses in the medical field. Chapter three describes comprehensively the experimental setup and work procedures that are adopted by this research. It also discusses the work fabrication and experimental works to produce the biocomposite films and characterization method to evaluate the properties of wound dressing material. Subsequently, chapter four discusses and evaluates thoroughly the results obtained from experimental work. Finally, chapter five presented a general conclusion and recommendation for further research based on the findings from this work.

CHAPTER TWO

LITERATURE REVIEW

2.1 INTRODUCTION

A suitable wound dressing material should extract exudates and toxic substances from the surfaces of the wound, facilitate gaseous exchange, protect the wound from bacterial infection, retain high moisture at the wound/dressing site, and it should be removed safely without damaging the wound. This chapter will extensively explain the type of wounds, wound healing process, the polysaccharides material, and the reason to be a suitable candidate for medical application, especially in wound dressing scaffold, membranes, and films. Starch is a type of polysaccharide, and this section will have an explained review on the structure and properties of starch and what research had reported about starch and its uses in the medical field. Many scholars have extensively studied halloysite nanotubes, so a review about halloysite nanotubes' structure, properties, and applications are also covered.

2.2 TYPE OF WOUNDS

Generally, wounds can be classified into two major types such as acute and chronic, as shown in Figure 2.1. Acute wound involving both the epidermis and superficial dermis, or full-thickness in which the subcutaneous layer is compromised (Driefke, Jayasuriya, & Jayasuriya, 2015). Conversely, chronic wounds occurred due to the complications of other disease processes such as foot ulcers from diabetes, pressure ulcers resulting from spinal cord injuries, and fungating or malignant wounds. The details of each classification are described in the sub-section below

In general, wounds can be categorized into two main sections acute and chronic, as shown in Figure 2.1

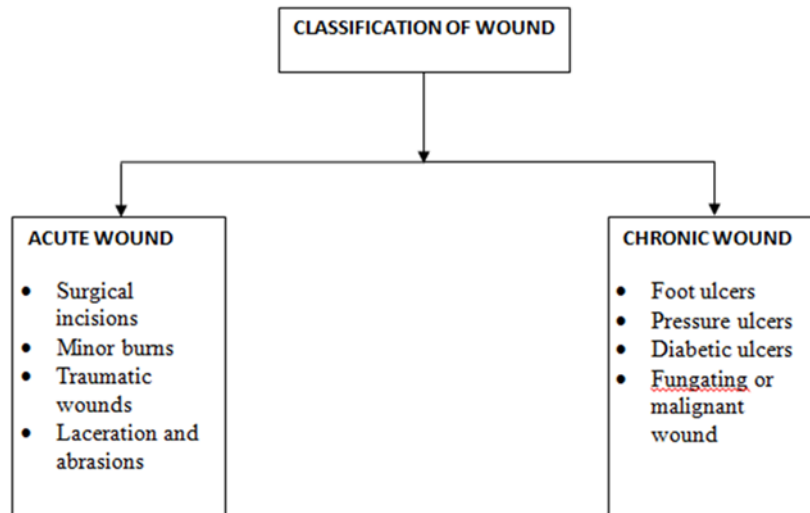


Figure 2.1: Wound classification

2.2.1 Chronic Wounds

Chronic wounds are characterized by cellular aging, recurrent infections, and delayed healing (Schultz et al., 2011). There are differences between acute wounds and chronic wounds. The wound healing process tends to heal acute wounds after 3 weeks, and chronic wounds take at least 3 months to continue. The healing of wounds, including acute and chronic wounds, is one of the significant clinical challenges of the world.

2.2.2 Acute Wounds

Minor burns, surgical incisions, and some traumatic injuries are examples of acute wounds with significant complications associated with each injury. In this research, the focus will be on acute wounds mostly. A critical wound is damage that occurs on the skin. The main difference between an acute wound and a chronic wound is that the acute